

Characterization and functionality of imidazolium ionic liquids modified magnetic nanoparticles

著者	Li Ying, Tang Ning, Inagaki Fuyuhiko, Mukai Chisato, Hayakawa Kazuichi
journal or publication title	Journal of Chemistry
page range	861021
year	2013-01-01
URL	http://hdl.handle.net/2297/35109

doi: 10.1155/2013/861021

Characterization and functionality of imidazolium ionic liquids-modified magnetic nanoparticles

Ying Li^{1,2}, Ning Tang^{1*}, Fuyuhiko Inagaki¹, Chisato Mukai¹, and Kazuichi Hayakawa¹

¹Institute of Medical, Pharmaceutical and Health Sciences, Kanazawa University, Kakuma-machi, Kanazawa, 920-1192, Japan

²Department of Chemical and Chemical Engineering, Henan Institute of Science and Technology, Xinxiang, Henan, 453003, P. R. China

Correspondence should be addressed to Ying Li and Kazuichi Hayakawa; rklxy@yahoo.com.cn, hayakawa@p.kanazawa-u.ac.jp

Abstract

1,3-dialkylimidazolium-based ionic liquids were chemically synthesized and bonded on the surface of magnetic nanoparticles (MNPs) with easily one-step reaction. The obtained six kinds of ionic liquid-modified MNPs were characterized with transmission electron microscopy, thermogravimetric analysis, magnetization and FTIR, which owned the high adsorption capacity due to the nanometer size and high-density modification with ionic liquids. Functionality of MNPs with ionic liquids greatly influenced the solubility of the MNPs with organic solvents depending on the alkyl chain length and the anions of the ionic liquids. Moreover, the obtained MNPs showed the specific extraction efficiency to organic pollutant, polycyclic aromatic hydrocarbons, while superparamagnetic property of the MNPs facilitated the convenient separation of MNPs from the bulks water samples.

Keywords: Ionic liquid, magnetic nanoparticle, multiple functions, polycyclic aromatic hydrocarbons

1. Introduction

Magnetic nanoparticles (MNPs) have potential application for material science and biomedicine because of their unique superparamagnetism and large surface area. MNPs can be functionalized by modifying their surfaces with various materials to achieve the

* Present affiliation: Hyogo College of Medicine, 1-1 Mukogawa-cho, Nishinomiya, Hyogo 663-8501, Japan

special purposes [1-4]. Coated shell-core MNPs with carbon, alumina, and surfactants have been recently used to preconcentrate inorganic/organic contaminants in environmental and biological samples [5-8]. Ionic liquids, which can be tuned by choosing of the cations and anions independently, exhibited unique physicochemical properties, such as tunable miscibility with water and organic solvents, and have potential applications as electrolyte materials, green solvents, catalysts and separation mediums [9-14]. N,N'-diallylimidazolium-based ionic liquids have also been used as extractant to highly enrich organic pollutants from aqueous samples in microextraction techniques, such as dispersed liquid-liquid microextraction and single drop microextraction, or to functionalize the stationary phase of chromatographic column and solid fiber membranes [15-21]. MNPs coated with ionic liquid was applied to preconcentrate polycyclic aromatic hydrocarbons (PAHs) in water samples through forming mixed hemimicelles on the surface of MNPs. However, it has been noted the coating of ionic liquid is noncovalent, which means that ionic liquid is more easily desorbed from surface and preconcentration of organic pollutants is strongly affected by the extraction parameters. In this work, a novel kind of modified MNPs with N,N'-dialkylimidazolium-based ionic liquids containing different alkyl chain lengths and inorganic anions were synthesized by covalent bonding. The functionalization of the resultant MNPs were confirmed by transmission electron microscopy (TEM), thermogravimetric analysis (TGA) and Fourier transform infrared spectra (FTIR). Although the naked and modified MNPs had similar saturation magnetizations, the obvious differences of solubility in water and organic solvents were observed. The modified MNPs were used to preconcentration the trace level of carcinogenic PAHs in environmental water samples. To the best of our knowledge, this is the first work about application of the chemically bonded ionic liquid-modified MNPs for detecting carcinogenic organic pollutants in environmental water samples.

2. Experimental

3-(2-Imidazolin-1-yl) propyltriethoxysilane was purchased from Sigma-Aldrich. 1-Chlorohexane, 1-chlorooctane and 1-chlorodecane were purchased from Tokyo Chemical Industry Co., Ltd (Japan). NaPF₆, FeCl₃·6H₂O and FeCl₂·4H₂O were purchased from Wako Pure Chemical Industries, Ltd. PAHs standards were purchased from Supelco (USA). Organic solvents are HPLC grade. A Milli-Q water purification system (USA) was used to prepare ultrapure water.

The magnetic iron oxide nanoparticles (MNPs) were synthesized by the Massart's method with minor changes (Scheme 1) [22]. Six kind of (3-triethoxysilylpropyl)-4,5-dihydroimidazolium (TIM) ionic liquids (1-hexyl-3-TIM

chloride (HTIMCl), 1-octyl-3-TIM chloride (OTIMCl), 1-decyl-3-TIM chloride (DTIMCl), 1-hexyl-3-TIM hexafluorophosphate (HTIMPF₆), 1-octyl-3-TIM hexafluorophosphate (OTIMPF₆), 1-decyl-3-TIM hexafluorophosphate (DTIMPF₆) were synthesized (Table 1). The synthesis method was as below (Scheme 1): a mixture of 3-(2-imidazolin-1-yl) propyltriethoxysilane and 1-chloroalkane was stirred at 120 °C for 8 h. Then the mixture was cooled to room temperature to afford 1-alkyl-3-(3-triethoxysilylpropyl)-4, 5-dihydroimidazolium chloride as an orange oil. To a solution of 1-alkyl-3-(3-triethoxysilylpropyl)-4, 5-dihydroimidazolium chloride in CH₃CN was added NaPF₆ at room temperature. After stirring for 5 min, the reaction mixture was filtrated, and the volatile were evaporated off to afford 1-alkyl-3-(3-triethoxysilylpropyl)-4, 5-dihydroimidazolium hexafluorophosphate. The resultants were colourless powders when alkyl were hexyl and decyl with melting point of 131-132 °C and 123-124 °C, respectively, while the resultant was an orange oil when the alkyl was octyl. The obtained ionic liquids were confirmed by FTIR, H-NMR and C-NMR. The ionic liquid-functional MNPs were obtained through adding a solution of the desired functionalized ionic liquid and 28% aqueous NH₃. After mechanical stirring for 36 h at room temperature, the ionic liquid-functionalized MNPs were magnetically separated, washed with EtOH and concentrated to dryness under reduced pressure (less than 1 mmHg) to give the desired product as black powders. The ionic liquid-modified MNPs are designated as MNP-X, where X is the abbreviation of the ionic liquid (Table 1).

Morphologies were observed by TEM (JEM-2010, Tokyo, Japan) and HRTEM images were obtained using the same transmission electron microscope. Thermogravimetric analysis (TGA) was done with a TG/DTA 6200 (SII Nano Technology, Tokyo, Japan). X-ray powder diffraction (XRD) was carried out on a Rigaku x-ray RINT2200 (Ultima, Tokyo, Japan) diffractometer with Cu K_α radiation ($\lambda = 0.1542$ nm). Magnetic properties were measured with a SQUID magnetometer (Quantum Design MPMS). FTIR were taken in KBr pressed pellets with a suitable ratio of MNP to KBr on a FTIR-8700 (shimadzu, Kyoto, Japan).

The functional MNPs were added to the filtered river water sample to enrich the organic pollutants, polycyclic aromatic hydrocarbons (PAHs), under the sonication effect. After that an NdFeB magnet was then utilized to collect the MNPs from samples, and then the enriched PAHs were eluted with hexane. 1 mL final solution was obtained after concentrating the elution solution and transferring the solvent to acetonitrile, analyzed with HPLC [23].

3. Results and Discussion

The structures of the ILs, MNPs and the functional MNPs were confirmed by the FTIR spectra (Figure 1, H-NMR and C-NMR spectra can be obtained from the support information). The peaks in the naked Fe_3O_4 and MNP-DTIMPF₆ at 558 cm^{-1} were due to the Fe-O group and the peaks in DTIMPF₆ and MNP-DTIMPF₆ at 850 cm^{-1} , 1654 cm^{-1} and 2931 cm^{-1} were due to the -P-F, -C=N- and C-H groups, respectively. These results demonstrated the successful bonding of DTIMPF₆ to the naked MNPs by covalent bonds. The peaks in the MNP-DTIMPF₆ at 2360 cm^{-1} might be due to the -C=O of CO₂ absorbed on the surface of MNP-DTIMPF₆.

TEM images showed the naked MNPs (Figure 2a) and a representative ionic liquid-modified MNPs (MNP-DTIMPF₆; Figure 2b, 2c) were quasi-spheres with a mean diameter of about 12 nm. The naked and modified MNPs showed no differences in shape or size. No changes on shape and size of the MNPs were observed after treatment with the water samples. Our modified MNPs differed from coated shell-core structure MNPs, which had a thick coated shell [4-7]. Elemental analysis data showed that the carbon contents of ionic liquid-modified MNPs ranged from 4.25 to 7.15 % depending on the alkyl chain length, whereas the carbon content of naked Fe_3O_4 was 0 % (Table 2). The N and H contents of naked Fe_3O_4 might come from air and water absorbed on the surface of MNPs.

Thermogravimetric analysis (TGA) of naked MNPs detected no significant peaks (Figure 3). There was a 3 % weight loss as the temperature increased from $100\text{ }^\circ\text{C}$ to $700\text{ }^\circ\text{C}$, which might be due to a loss of absorbed water. In contrast, the functionalized MNPs lost weight in two steps. The first step occurred over the range $100\text{-}250\text{ }^\circ\text{C}$, and might also be due to the loss of absorbed water. The second step consisted of a weight loss of about 5 % over the range $250\text{-}450\text{ }^\circ\text{C}$, and might be due to the burning of bonded ionic liquids. At higher temperatures of $450\text{-}700\text{ }^\circ\text{C}$, the weight remained constant, implying the presence of only Fe_3O_4 left within the temperature range.

The XRD patterns of naked Fe_3O_4 and a representative modified MNP (MNP-DTIMPF₆; Figure 4) had six characteristic peaks ($2\theta = 30.1, 35.5, 43.1, 53.4, 57.0$ and 62.6°), corresponding to the Miller indices (220), (311), (400), (422), (511) and (440), respectively. The same peaks were observed for all the modified MNPs. These peaks were in agreement with those in the Mineral Powder Diffraction File Data Book (International Center for Diffraction Data, No. 19-629), indicating that the MNPs were

pure Fe_3O_4 with a spinel structure. Also, the binding process did not result in a phase change of the modified MNPs. Plots of magnetization versus magnetic field (M-H loop) at 25 °C, obtained with a superconducting interference device (SQUID), showed very weak hysteresis in both naked Fe_3O_4 and MNP-DTIMPF₆ nanoparticles (Figure 5), indicating that the modified MNPs were superparamagnetic. The saturation magnetization (M) of modified MNPs (60.8 to 63.2 emu g⁻¹) was only slightly less than that of naked Fe_3O_4 nanoparticles (65.8 emu g⁻¹), indicating that it was little affected by modification of the surface of MNPs. Superparamagnetism of ionic liquid-modified MNPs was an advantage because it prevented the aggregation of MNPs, so that MNPs can be dispersed into a solution again after removal of an external magnet.

The solubility of MNPs strongly depended on the alkyl chain length and anions of the ionic liquid. Modification of MNPs with 1-butyl-3-TIM chloride greatly increased their solubility in water and polar organic solvents [24]. In the present work, the modified MNPs were not soluble in water regardless of the alkyl chain and anions, although they could be dispersed ultrasonically. However, they were soluble and stable in polar organic solvents (*e.g.*, MeOH, EtOH and CH_2Cl_2) to varying degrees depending on the solvent. In strong polar solvents like MeOH and EtOH, the modified MNPs with chloride as anion were more soluble than those with PF_6^- as anion. The solubility decreased with increasing alkyl chain length: hexyl>octyl>decyl. On the other hand, in CH_2Cl_2 , a weak polar solvent, the modified MNPs with PF_6^- as anion were more soluble, with solubility increasing with increasing chain length: decyl>octyl>hexyl. Strangely, MNP-OTIMPF₆ has highest solubility in both strong and weak polar solvents (Figure 6). Its unexpected high solubility in organic solvent might be related in some way to its low melting point (OTIMPF₆ was orange-colored liquid while HTIMPF₆ and DTIMPF₆ were colorless powder). Neither naked MNP nor modified MNPs were soluble in nonpolar organic solvents, such as hexane.

PAHs were designated as the priority monitoring pollutants due to their potential carcinogenic or mutagenic properties. In the present work, ten PAHs with 4~6 fused rings (fluoranthene (Flu), pyrene (Pyr), benz[*a*]anthracene (BaA), chrysene (Chr), benzo[*b*]fluoranthrene (BbF), benzo[*k*]fluoranthrene (BkF), benzo[*a*]pyrene (BaP), dibenz[*a,h*]anthracene (DBA), benzo[*g,h,i*]perylene (BgPe) and indeno[1,2,3-*cd*]pyrene (IDP)) were selected as target to examine the functionality of the MNPs. The results of the spiked river water samples with PAHs standards were compared with the original water samples. Recoveries of PAHs from spiked water samples with ionic liquid-modified MNPs were much higher

than those of the naked Fe₃O₄, clearly demonstrating the extraction ability of imidazolium-based ionic liquids of the modified MNPs to PAHs. Ionic liquid-modified MNPs with hexafluorophosphate anion had much higher recoveries than MNPs with chloride anion when the alkyl was hexyl, while they had similar recoveries when the alkyl was octyl or decyl. In general, recoveries of PAHs were higher for MNPs with PF₆⁻ anion than that with Cl⁻ anion. π - π and hydrophobic interactions between PAHs and N,N'-dialkylimidazolium-based ionic liquids were presented [19]. The main interaction should be π - π interaction when the alkyl is hexyl. The anions greatly affected the property of N,N'-dialkylimidazolium-based ionic liquid. However, the property of ionic liquid gradually depended on the cation with increasing of alkyl chain length and hydrophobic interaction played an important role to preconcentration. Hence, a better detection efficiency might be improved if MNPs were modified with ionic liquids with longer alkyl chain, *e.g.* octadecyl, and PF₆⁻ or more hydrophobic anions were provided. As a demonstration, MNP-DTIMPF₆ was found to efficiently preconcentrate several PAHs (Flu, Pyr, BaA, Chr, BbF, BkF and BaP) from a river water sample (Figure 7). A similar chromatogram was obtained with the river water sample spiked with PAH standard solutions, confirming the detections.

4. Conclusion

1-alkyl-3-(3-triethoxysilylpropyl)-4,5-dihydroimidazolium anion ionic liquids were synthesized and successfully bonded to the MNPs. Measurement of IR, NMR, TGA, TEM and elemental analysis confirmed the structures. XRD and MPMS analysis illustrated the Fe₃O₄ core of the MNPs with superparamagnetism. Functionality of MNPs with ionic liquids greatly influenced their solubility in organic solvents and facilitated the specific extraction capability to organic pollutants.

Acknowledgement

This work was supported in part by a Grant-in-Aid for scientific research from the Ministry of Education, Science, Sport and Culture and by funds from the Ministry of Environment, Japan. We thank Prof. M. Okuno for XRD measurement and Prof. T. Yamagishi for his help of TGA analysis. Y. Li was supported by a Postdoctoral Fellowship for Foreign Researchers from the Japan Society for the Promotion of Sciences (JSPS).

References

[1] R. Hao, R. Xing, Z. Xu, Y. Hou, S. Gao, S. Sun, "Synthesis, functionalization, and biomedical applications of multifunctional magnetic nanoparticles," *Advanced Materials*,

vol. 22, no. 25, pp. 2729-2742, 2010.

[2] M. Safarikova, P. Lunackova, K. Komarek, T. Hubka, I. Safarik, "Preconcentration of middle oxyethylated nonylphenols from water samples on magnetic solid phase," *Journal of Magnetism and Magnetic Materials*, vol. 311, no. 1, pp. 405-408, 2007.

[3] C. Xu, K. Xu, H. Gu, R. Zheng, H. Liu, X. Zhang, Z. Guo, B. Xu, "Dopamine as A Robust Anchor to Immobilize Functional Molecules on the Iron Oxide Shell of Magnetic Nanoparticles," *Journal of the American Chemical Society*, vol. 126, no. 32, pp. 9938-9939, 2004.

[4] R. D. Palma, S. Peeters, M. J. V. Bael, H. V. D. Rul, K. Bonroy, W. Laureyn, J. Mullens, G. Borghs, G. Maes, "Silane Ligand Exchange to Make Hydrophobic Superparamagnetic Nanoparticles water-Dispersible," *Chemical Materials*, vol. 19, no. 7, pp. 1821-1831, 2007.

[5] S. X. Zhang, H. Y. Niu, Z. J. Hua, Y. Q. Cai, Y. L. Shi, "Preparation of carbon coated Fe₃O₄ nanoparticles and their application for solid-phase extraction of polycyclic aromatic hydrocarbons from environmental water samples," *Journal of Chromatography A*, vol. 1217, no. 29, pp. 4757-4764, 2010.

[6] L. Sun, C. Z. Zhang, L. Chen, J. Liu, H. Y. Jin, H. Y. Xu, L. Ding, "Preparation of alumina-coated magnetite nanoparticle for extraction of trimethoprim from environmental water samples based on mixed hemimicelles solid-phase extraction," *Analytica Chimica Acta*, vol. 638, no. 2, pp. 162-168, 2009.

[7] J. S. Suleiman, B. Hu, H. Y. Peng, C. Z. Huang, "Separation/preconcentration of trace amounts of Cr, Cu and Pb in environmental samples by magnetic solid-phase extraction with Bismuthiol-II-immobilized magnetic nanoparticles and their determination by ICP-OES," *Talanta*, vol. 77, no. 5, pp. 1579-1583, 2009.

[8] A. Ballesteros-Gómez, S. Rubio, "Hemimicelles of Alkyl Carboxylates Chemisorbed onto Magnetic Nanoparticles: Study and Application to the Extraction of Carcinogenic Polycyclic Aromatic Hydrocarbons in Environmental Water Samples," *Analytical Chemistry*, vol. 81, no. 21, pp. 9012-9020, 2009.

[9] M. Smiglak, Andeas Metlen, R. D. Rogers, "The Second Evolution of Ionic Liquids: From Solvents and Separations to Advanced Materials-Energetic Examples from the Ionic Liquid Cookbook," *Accounts of Chemical Research*, vol. 40, no. 11, pp. 1182-1192, 2007.

- [10] M. Tobiszewski, A. Mechlińska, B. Zygmunt, J. Namieśnik, "Green analytical chemistry in sample preparation for determination of trace organic pollutants," *Trends in Analytical Chemistry*, vol. 28, no. 8, pp. 943-951, 2009.
- [11] K. Yamaguchi, C. Yoshida, S. Uchida, N. Mizuno, "Peroxytungstate Immobilized on Ionic Liquid-Modified Silica as a Heterogeneous Epoxidation Catalyst with Hydrogen Peroxide," *Journal of the American Chemical Society* vol. 127, no. 2, pp. 530-531, 2005.
- [12] S. Shylesh, V. Schünemann, W. R. Thiel, "Magnetically Separable Nanocatalysts: Bridges between Homogeneous and Heterogeneous Catalysis," *Angewandte Chemie International Edition*, vol. 49, no. 20, pp. 3428-3459, 2010.
- [13] T. Torimoto, T. Tsuda, K. Okazaki, S. Kuwabata, "New Frontiers in Materials Science Opened by Ionic Liquids," *Advanced Materials*, vol. 22, pp. 1196-1221, 2010.
- [14] X. X. Han, D. W. Armstrong, "Ionic Liquids in Separations" *Accounts of Chemical Research*, vol. 40, no. 11, pp. 1079-1086, 2007.
- [15] S. G. Lee, "Functionalized imidazolium salts for task-specific ionic liquids and their applications. Chem. Commun.," *Chemical Communication*, no. 10, pp. 1049–1063, 2006.
- [16] X. J. Sun, Y. L. Zhu, P. Wang, J. Li, C. Y. Wu, J. Xing, "High temperature and highly selective stationary phases of ionic liquid bonded polysiloxanes for gas chromatography," *Journal of Chromatography A*, vol. 1218, no. 6, pp. 833–841, 2011.
- [17] W. Y. Zhao, M. Han, S. G. Dai, J. Xu, P. Wang, "Ionic liquid-containing semipermeable membrane devices for monitoring the polycyclic aromatic hydrocarbons in water," *Chemosphere*, vol. 62, no. 10, pp. 1623-1629, 2006.
- [18] K. P. Huang, G. R. Wang, B. Y. Huang, C. Y. Liu, "Preparation and application of ionic liquid-coated fused-silica capillary fibers for solid-phase microextraction," *Analytica Chimica Acta*, vol. 645, no. 1-2, pp. 42-47, 2009.
- [19] H. D. Qiu, M. Takafuji, X. Liu, S. X. Jiang, H. Ihara, "Investigation of π - π and ion-dipole interactions on 1-allyl-3-butylimidazolium ionic liquid-modified silica stationary phase in reversed-phase liquid chromatography," *Journal of Chromatography A*, vol. 1217, no. 32, , 5190-5196, 2010.
- [20] C. Yao, W. R. Pitner, J. L. Anderson, "Ionic Liquids Containing the Tris(pentafluoroethyl)trifluorophosphate Anion: a New Class of Highly Selective and

Ultra Hydrophobic Solvents for the Extraction of Polycyclic Aromatic Hydrocarbons Using Single Drop Microextraction,” *Analytical Chemistry*, vol. 81, no. 12, pp. 5054–5063, 2009.

[21] R. J. Soukup-Hein, M. M. Warnke, D. W. Armstrong, “Ionic Liquids in Analytical Chemistry,” *Annual Review of Analytical Chemistry*, vol. 2, pp. 145–168, 2009.

[22] R. Massart, “Preparation of aqueous magnetic liquid in alkaline and acidic media,” *IEEE Transactions on Magnetic*, vol. 17, no. 2, pp. 1247-1248, 1981.

[23] Y. Li, S. Yoshida, Y. Chondo, H. Nassar, N. Tang, Y. Araki, A. Toriba, T. Kameda, K. Hayakawa, “On-line Concentration and Fluorescence Determination HPLC for Polycyclic Aromatic Hydrocarbons in Seawater Samples and Its Application to Japan Sea,” *Chemical & Pharmaceutical Bulletin*, vol. 64, no. 4, pp. 531-535, 2012.

[24] R. Abu-Reziq, D. S. Wang, M. Post, **H. Alper**, “Platinum Nanoparticles Supported on Ionic Liquid-Modified Magnetic Nanoparticles: Selective Hydrogenation Catalysts,” *Advanced Synthesis Catalysis*, vol. 349, no. 13, pp. 2145-2150, 2007.

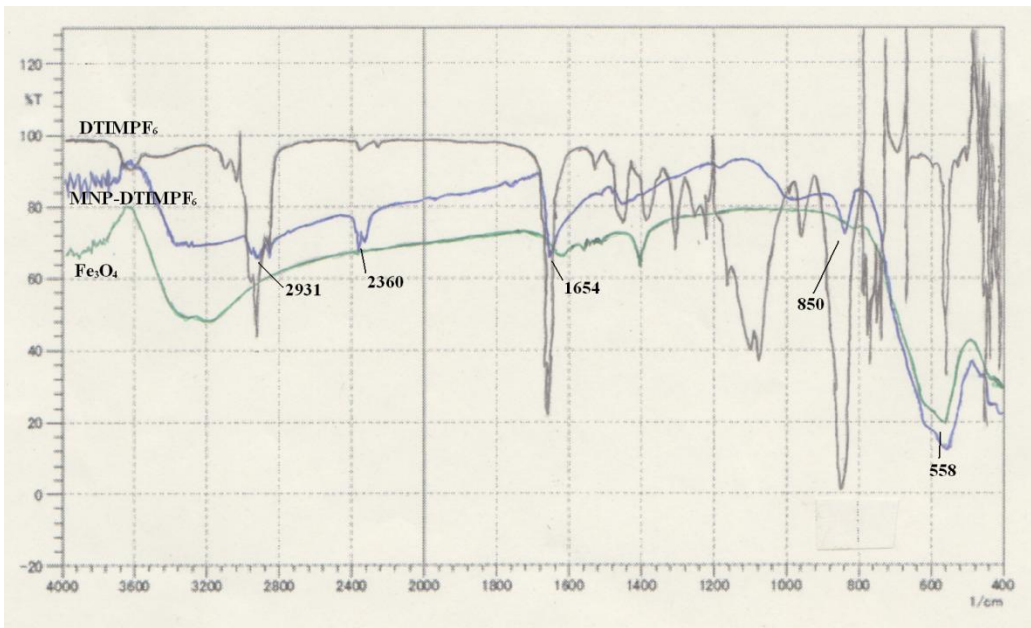


Figure 1: IR spectra of Fe₃O₄, DTIMPF₆ and MNP-DTIMPF₆

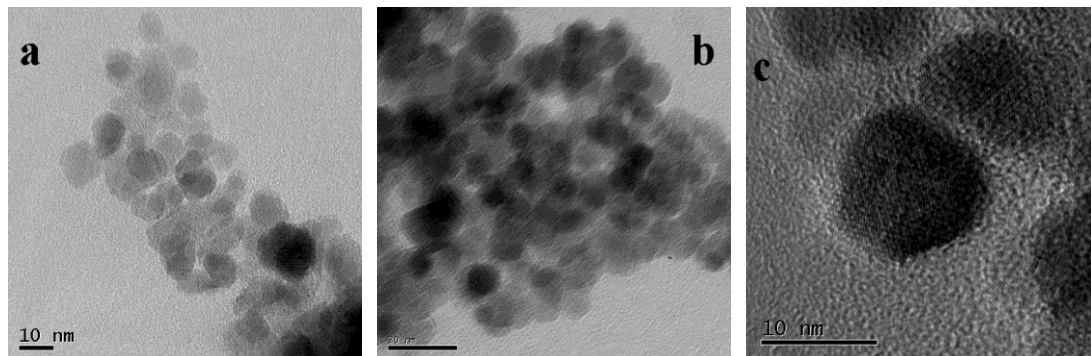


Figure 2: a) TEM of Fe₃O₄, b) TEM of MNP-DTIMPF₆, c) HRTEM of MNP-DTIMPF₆

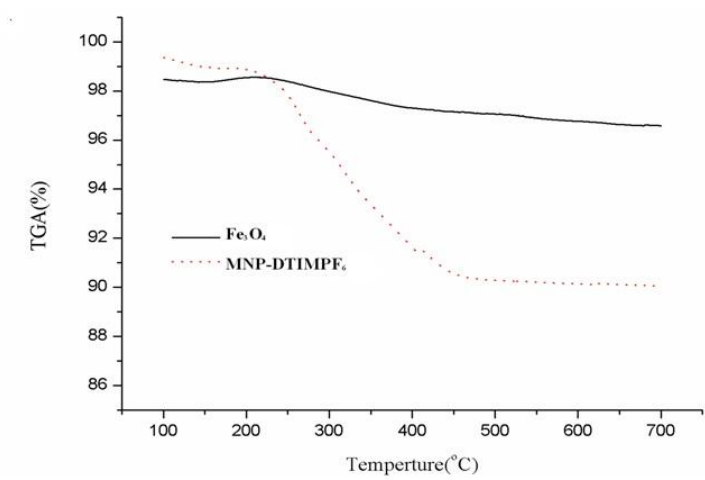


Figure 3: TGA of Fe₃O₄ and MNP-DTIMPF₆

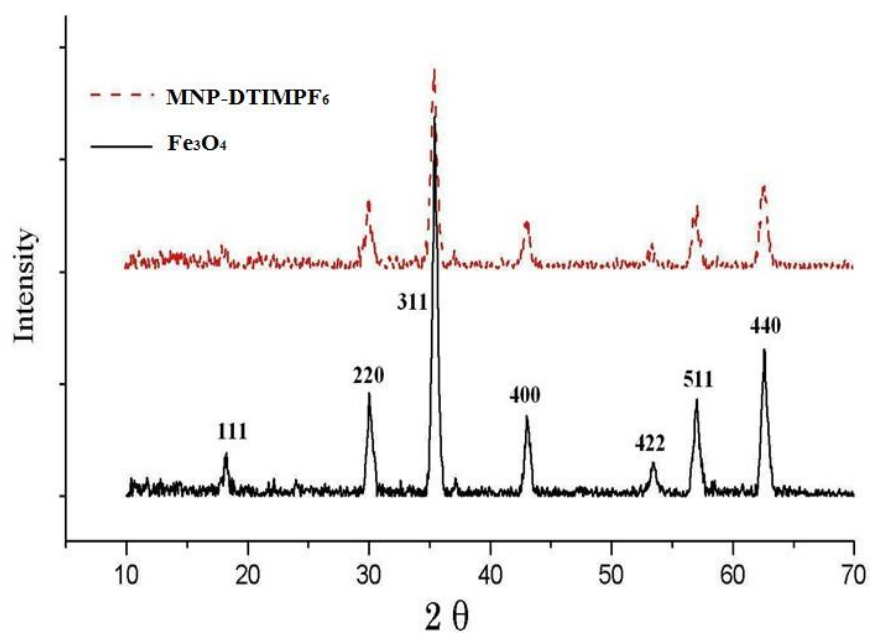


Figure 4: X-ray diffraction patterns of Fe₃O₄ and MNP-DTIMPF₆ (Miller indices of the peaks are indicated).

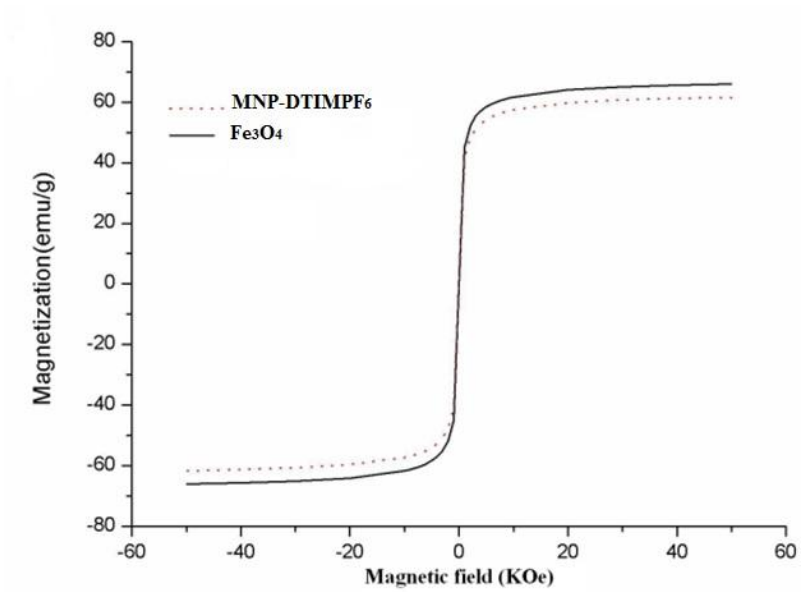


Figure 5: Magnetization vs. magnetic field for Fe₃O₄ and MNP-DTIMPF₆ at 25°C.

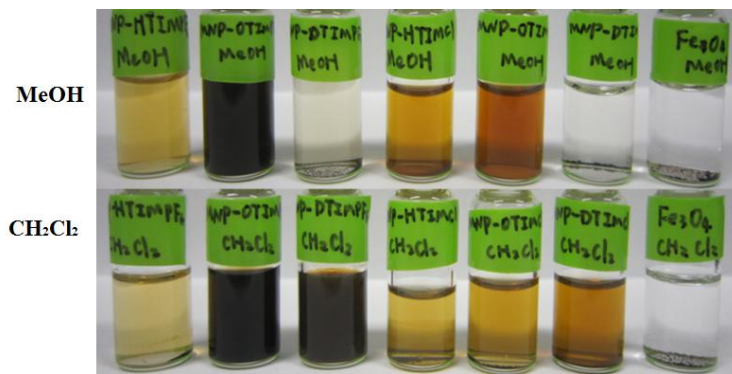


Figure 6: Solubility of the naked and modified MNPs in methanol and CH₂Cl₂.

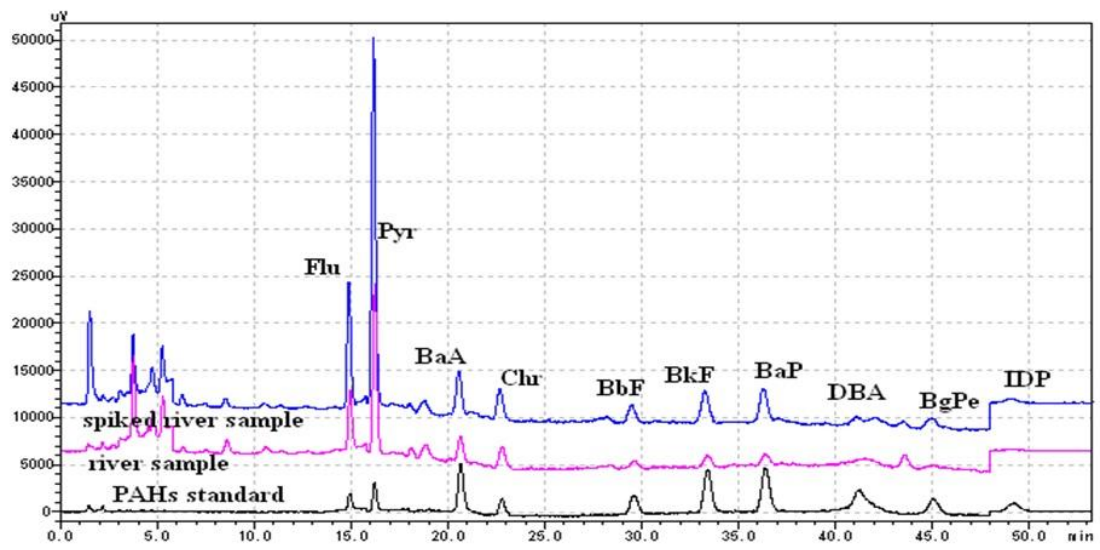


Figure 7: Chromatograms of PAHs standard, river water sample and spiked river water sample


Table 1: Ionic liquids synthesized for this study

Abbrev.	Ionic liquid	M [g mol ⁻¹]
HTIMCl	1-hexyl-3-TIM chloride*	504
OTIMCl	1-octyl-3-TIM chloride	532
DTIMCl	1-decyl-3-TIM chloride	560
HTIMPF ₆	1-hexyl-3-TIM hexafluorophosphate	395
OTIMPF ₆	1-octyl-3-TIM hexafluorophosphate	423
DTIMPF ₆	1-decyl-3-TIM hexafluorophosphate	451



TIM: (3-triethoxysilylpropyl)-4,5-dihydroimidazolium

Table 2: Results of elemental analysis and TGA of MNPs



MNPs	Elemental analysis (%)			TGA(%)
	C	H	N	A
Fe ₃ O ₄	0.00	0.60	0.43	
MNP-HTIMPF ₆	4.25	1.08	0.89	4.8
MNP-OTIMPF ₆	5.42	1.28	1.33	4.5
MNP-DTIMPF ₆	6.35	1.45	0.98	6.5
MNP-HTIMCl	4.54	1.10	0.99	4.8
MNP-OTIMCl	4.99	1.17	0.97	4.6
MNP-DTIMCl	7.15	1.55	1.09	8.5



(2)

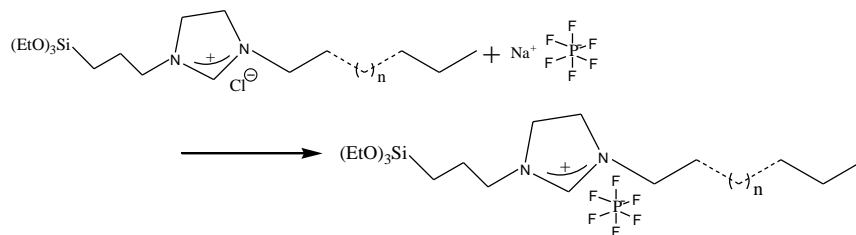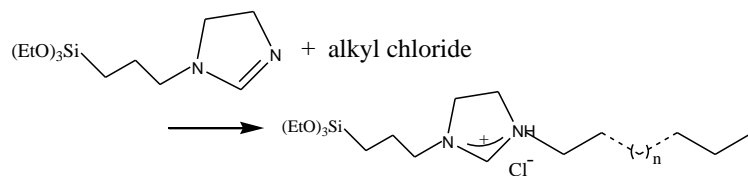

(3)

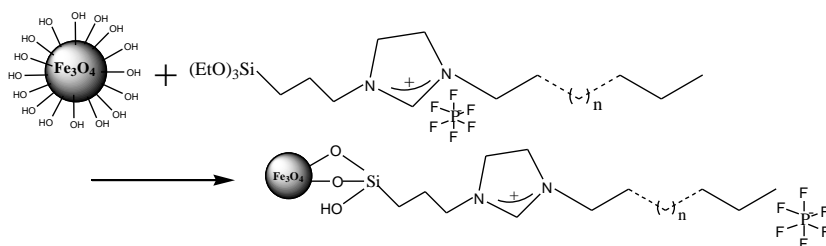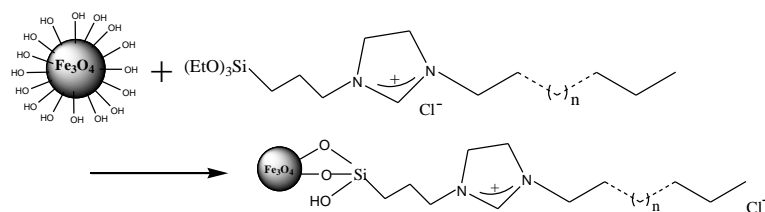

Scheme 1. Synthesis of ionic liquid-modified MNPs (alkyl=hexyl, octyl and decyl)